



IESNA LM-80-2008

MEASURING LUMEN MAINTENANCE OF LED LIGHT SOURCES

MEASUREMENT AND TEST REPORT

For

Xiamen Dacol Photoelectronics Technology Co.,Ltd.

8021 Xiang' an West Road(Xiang' an)industrial zone,Torch Hi-Tech Industrial Development Zone,Xiamen City,Fujian,China

Model: 2835

Report Type: 6000 Hours Test Report		Product Type: LED Package	
Test Engineer:	Daniel Duan <i>Daniel Duan</i>		
Report Number:	R2DG141201054-10		
Test Date:	2014-12-25 to 2015-09-11		
Report Date:	2015-09-17		
Reviewed By:	Jeanne Han /EE Manager <i>Jeanne Han</i>		
Prepared By:	Bay Area Compliance Laboratories Corp. (Dongguan). Pu Long Cun 69, Puxinghu Industrial Area, Tangxia Town, Dongguan, Guangdong, P.R.China. Tel: +86-0769-86858888 Fax:+86-0769-86858588		

Note: The test data was only valid for the test sample(s). This test report is prepared for the customer shown above and for the device described herein. It may not be duplicated or used in part without prior written consent from Bay Area Compliance Laboratories Corp. (Dongguan).

This report is valid only with a valid digital signature. The digital signature may be available only under the Adobe software above version 7.0.

TABLE OF CONTENTS

1 - GENERAL INFORMATION.....	3
1.1 DESCRIPTION OF LED LIGHT SOURCES	3
1.2 STANDARDS USED:.....	3
1.3 TEST FACILITY	3
1.4 DESCRIPTION OF AUXILIARY EQUIPMENT	3
1.5 OPERATING CYCLE.....	4
1.6 AMBIENT CONDITIONS	4
1.7 PHOTOMETRY MEASUREMENT UNCERTAINTY	4
1.8 SAMPLE SET	5
2 - SUMMARY OF TEST RESULT	6
3 - TEST DATA	7
3.1 DATA SET 1, 55°C, 100mA (LUMEN MAINTENANCE)	7
3.2 DATA SET 1, 55°C, 100mA (CHROMATICITY SHIFT)	8
3.3 DATA SET 2, 85°C, 100mA (LUMEN MAINTENANCE)	9
3.4 DATA SET 2, 85°C, 100mA (CHROMATICITY SHIFT)	10
3.5 DATA SET 3, 105°C, 100mA (LUMEN MAINTENANCE)	11
3.6 DATA SET 3, 105°C, 100mA (CHROMATICITY SHIFT)	12
ATTACHMENT A – EUT PHOTO	13
A.1 MECHANICAL DIMENSIONS (TA = 25°C).....	13
A.2 EUT PHOTO	13

1 - GENERAL INFORMATION

1.1 Description of LED Light Sources

Devices tested

Part Number: 2835
 Part Type: LED Package
 Nominal CCT: 3500K

1.2 Standards Used:

- IESNA LM-80-08: IES Approved Method for Measuring Lumen Maintenance of LED Light Sources.
- ENERGY STAR® Program Guidance Regarding LED Package, LED Array and LED Module Lumen Maintenance Performance Data Supporting Qualification of Lighting Products(This test method was not accredited by IAS)

1.3 Test Facility

The testing facility used by Bay Area Compliance Laboratories Corp. (Dongguan). is located at Pu Long Cun 69, Puxinghu Industrial Area, Tangxia Town, Dongguan, Guangdong, P.R.China.

1.4 Description of Auxiliary Equipment

Device	Manufacture	Model No	Serial No	Test Range	Calibration date	Calibration due date
Integral Sphere	EVERFINE	Diameter 0.3m	1011119	380-780nm, Diameter:0.3m,0-1999Lumen	2015-03-25	2016-03-25
Programmable Test Power for LEDs	EVERFINE	LED300E	1008002	15V/2000mA	2015-03-05	2016-03-05
High accuracy array spectroradiometer	EVERFINE	HAAS-2000	1012016T	380-780nm	2015-03-25	2016-03-25
Standard Light Source	EVERFINE	D062	1011093	N/A	2015-08-05	2016-08-05
Precision digital stabilized DC power supply	EVERFINE	WY605	G115987C J7321114	300VA	2015-03-05	2016-03-05
Multilayer aging machine	BACL	B2-270	20022	25℃~110℃	2014-10-27	2015-10-27
Digital CC&CV DC Power Supply	EVERFINE	WY5015	11060010	(50V/15A)	2015-03-05	2016-03-05
Digital CC&CV DC Power Supply	EVERFINE	WY5015	11090008	(50V/15A)	2015-07-08	2016-07-07

Device	Manufacture	Model No	Serial No	Test Range	Calibration date	Calibration due date
Digital CC&CV DC Power Supply	EVERFINE	WY5015	11060002	(50V/15A)	2015-7-8	2016-7-7

1.5 Operating Cycle

Samples are driven with a constant direct current (DC)

1.6 Ambient Conditions

For lumen maintenance test, samples were operated in thermal chambers with minimal ambient airflow. For long term reliability test, the case temperature was controlled by mounting several thermocouples on a sample reliability stress board at the designated thermal measurement point, as shown in APPENDIX. The ambient temperature T_A was measured by several thermocouples at a distance of 5 mm above the reliability test board. The relative humidity within chamber was less than 65%.

For photometry measurement, temperature was set to $25^{\circ}\text{C} \pm 2^{\circ}\text{C}$, RH <65%.

1.7 Photometry Measurement Uncertainty

The uncertainty of the light output measurements is $U=1.59\%$ ($K=2$), at the 95% confidence level. The uncertainty of the correlated color temperature measurements is $U=21\text{K}$ ($K=2$), at the 95% confidence level. This calibration results traceable to the NATIONAL INSTITUTE OF METROLOGY (NIM).

1.8 Sample Set

Sampling Method:

LED samples for IESNA LM-80 testing consist of units built from a minimum of three manufacturing lots with each manufacturing lot built from different wafer lots built on non-consecutive days.

These manufacturing lots are picked to represent a wide parametric distribution.

Each Sample is soldered to all of the reliability stress boards for a given set of IESNA LM-80 tests.

Sample Size:

Total 75Pcs;

Each Ts test condition 25Pcs

The samples tested at Ts 55°C, Ts 85°C and Ts 105°C were received at 2014-12-01 and tested during 2014-12-25 to 2015-09-11. The samples were numbered from 1to 25, 26 to 50 and 51 to 75

Data Set 1: 55°C, 100mA

Part Number:	2835
Number of Units:	25
Actual Case Temperature(T _S):	T _S =54.1°C
Actual Ambient Temperature(T _A):	T _A =52.6°C
Life Test Drive Current:	I _F = 100mA
Measurement Current:	I _F = 100mA

Data Set 2: 85°C,100mA

Part Number:	2835
Number of Units:	25
Actual Case Temperature(T _S):	T _S =83.6°C
Actual Ambient Temperature(T _A):	T _A =82.5°C
Life Test Drive Current:	I _F =100mA
Measurement Current:	I _F = 100mA

Data Set 3: 105°C, 100mA

Part Number:	2835
Number of Units:	25
Actual Case Temperature(T _S):	T _S =103.6°C
Actual Ambient Temperature(T _A):	T _A =102.3°C
Life Test Drive Current:	I _F = 100mA
Measurement Current:	I _F = 100mA

2 - SUMMARY OF TEST RESULT

Data Set:	Data Set 1, 55°C, 100mA
Number of Units:	25
Failures Observed:	0
Test Interval and Test Duration:	0h,1000h,2000h,3000h,4000h,5000h,6000h
Average. Lumen Maintenance at 6000 hours:	97.15%
Average Chromaticity Shift at 6000 hours ($\Delta u'v'$):	0.0023
Reported TM-21 L ₇₀ Lifetime:	>36,000hours

Data Set:	Data Set 2, 85°C, 100mA
Number of Units:	25
Failures Observed:	0
Test Interval and Test Duration:	0h,1000h,2000h,3000h,4000h,5000h,6000h
Average. Lumen Maintenance at 6000 hours:	96.79%
Average Chromaticity Shift at 6000 hours($\Delta u'v'$):	0.0023
Reported TM-21 L ₇₀ Lifetime:	>36,000hours

Data Set:	Data Set 3, 105°C, 100mA
Number of Units:	25
Failures Observed:	0
Test Interval and Test Duration:	0h,1000h,2000h,3000h,4000h,5000h,6000h
Average. Lumen Maintenance at 6000 hours:	95.81%
Average Chromaticity Shift at 6000 hours($\Delta u'v'$):	0.0027
Reported TM-21 L ₇₀ Lifetime:	>36,000hours

3 - Test Data

3.1 Data Set 1, 55°C, 100mA (Lumen Maintenance)


No.	V _F (V)	Φ(lm)	Lumen Maintenance (%)					
	0hr(Initial)		1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
1	9.147	110.8	99.91	99.46	98.74	98.10	97.20	96.75
2	9.065	113.3	100.09	99.65	98.76	98.23	97.62	97.18
3	9.179	110.2	99.73	99.18	98.64	98.09	97.19	97.10
4	9.140	110.0	99.82	99.36	98.82	98.18	97.18	96.82
5	9.212	110.3	100.27	100.00	99.46	99.00	98.91	97.19
6	9.242	109.2	100.09	99.63	99.18	98.35	97.53	97.07
7	9.415	107.4	100.09	99.53	98.88	98.04	97.11	96.83
8	9.240	111.4	100.09	99.55	99.01	98.20	97.40	96.86
9	9.367	108.1	100.19	99.63	98.98	98.52	97.41	97.04
10	9.206	111.4	100.27	100.00	99.37	98.74	98.20	97.76
11	9.300	107.2	100.28	99.91	99.16	98.32	97.95	97.48
12	9.217	109.6	99.91	99.54	99.00	98.45	97.45	96.72
13	9.237	110.2	100.09	99.64	99.09	98.73	97.28	97.01
14	9.239	109.7	100.18	99.64	99.00	98.36	97.81	97.36
15	9.022	111.4	100.18	99.82	99.37	98.83	97.49	96.95
16	9.403	107.8	100.28	100.00	99.07	98.42	97.77	97.31
17	9.412	106.9	99.81	99.35	98.69	98.04	97.29	97.10
18	9.430	107.3	100.19	99.72	98.79	98.51	97.86	97.30
19	9.243	109.8	100.09	99.54	99.00	98.18	97.27	97.09
20	9.137	111.6	100.27	99.82	99.28	98.75	98.03	97.67
21	9.216	109.6	100.09	99.27	98.72	98.27	97.72	97.35
22	9.404	107.6	100.19	99.54	98.98	97.96	97.58	97.21
23	9.143	110.5	100.09	99.64	99.19	98.55	98.01	97.65
24	9.150	110.1	99.91	99.46	98.82	98.37	97.18	97.00
25	9.408	108.1	100.00	99.44	98.61	97.87	97.22	96.85
Ave.	9.247	109.6	100.08	99.61	98.98	98.36	97.59	97.15
Med.	9.237	109.8	100.09	99.63	99.00	98.35	97.49	97.10
st dev	0.1169	1.6633	0.1581	0.2213	0.2386	0.2903	0.4181	0.2867
Min.	9.022	106.9	99.73	99.18	98.61	97.87	97.11	96.72
Max.	9.430	113.3	100.28	100.00	99.46	99.00	98.91	97.76

TM-21 Projection:

Test Duration: 6000 hours
Failures Observed: 0
 α : 6.180E-06
 β : 1.008
Calculated L₇₀: 59,000 hours
Reported L₇₀: >36,000hours

3.2 Data Set 1, 55°C, 100mA (Chromaticity Shift)

No.	u'	v'	CCT(K)	Chromaticity Shift ($\Delta u'v'$)					
	0hr(Initial)			1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
1	0.2364	0.5140	3450	0.0004	0.0009	0.0014	0.0017	0.0022	0.0026
2	0.2357	0.5164	3444	0.0002	0.0005	0.0009	0.0014	0.0016	0.0022
3	0.2356	0.5160	3451	0.0004	0.0007	0.0012	0.0016	0.0018	0.0022
4	0.2363	0.5141	3451	0.0006	0.0009	0.0014	0.0017	0.0021	0.0023
5	0.2370	0.5170	3401	0.0003	0.0004	0.0007	0.0011	0.0016	0.0018
6	0.2364	0.5154	3434	0.0004	0.0009	0.0013	0.0017	0.0021	0.0023
7	0.2369	0.5170	3405	0.0004	0.0006	0.0011	0.0014	0.0018	0.0021
8	0.2360	0.5177	3423	0.0005	0.0009	0.0012	0.0016	0.0021	0.0023
9	0.2370	0.5165	3407	0.0004	0.0006	0.0010	0.0013	0.0018	0.0021
10	0.2369	0.5170	3405	0.0004	0.0005	0.0009	0.0012	0.0016	0.0021
11	0.2359	0.5137	3467	0.0003	0.0006	0.0011	0.0016	0.0020	0.0023
12	0.2368	0.5154	3421	0.0004	0.0008	0.0012	0.0016	0.0019	0.0023
13	0.2358	0.5162	3446	0.0006	0.0010	0.0015	0.0018	0.0021	0.0025
14	0.2358	0.5143	3466	0.0004	0.0007	0.0011	0.0013	0.0018	0.0023
15	0.2355	0.5151	3465	0.0004	0.0008	0.0014	0.0017	0.0021	0.0024
16	0.2353	0.5172	3450	0.0003	0.0005	0.0009	0.0013	0.0017	0.0021
17	0.2354	0.5138	3482	0.0005	0.0009	0.0015	0.0019	0.0025	0.0029
18	0.2362	0.5154	3441	0.0004	0.0006	0.0010	0.0014	0.0018	0.0021
19	0.2362	0.5137	3459	0.0006	0.0009	0.0014	0.0018	0.0022	0.0025
20	0.2361	0.5154	3443	0.0004	0.0006	0.0009	0.0013	0.0018	0.0021
21	0.2355	0.5159	3457	0.0004	0.0007	0.0010	0.0014	0.0018	0.0021
22	0.2373	0.5160	3403	0.0005	0.0007	0.0012	0.0016	0.0020	0.0023
23	0.2359	0.5153	3451	0.0005	0.0007	0.0012	0.0017	0.0021	0.0023
24	0.2347	0.5136	3506	0.0006	0.0009	0.0014	0.0018	0.0021	0.0026
25	0.2356	0.5169	3443	0.0006	0.0007	0.0013	0.0016	0.0021	0.0025
Ave.	0.2361	0.5156	3443	0.0004	0.0007	0.0012	0.0015	0.0019	0.0023
Med.	0.2360	0.5154	3446	0.0004	0.0007	0.0012	0.0016	0.0020	0.0023
st dev	0.0006	0.0013	26.0987	0.0001	0.0002	0.0002	0.0002	0.0002	0.0002
Min.	0.2347	0.5136	3401	0.0002	0.0004	0.0007	0.0011	0.0016	0.0018
Max.	0.2373	0.5177	3506	0.0006	0.0010	0.0015	0.0019	0.0025	0.0029

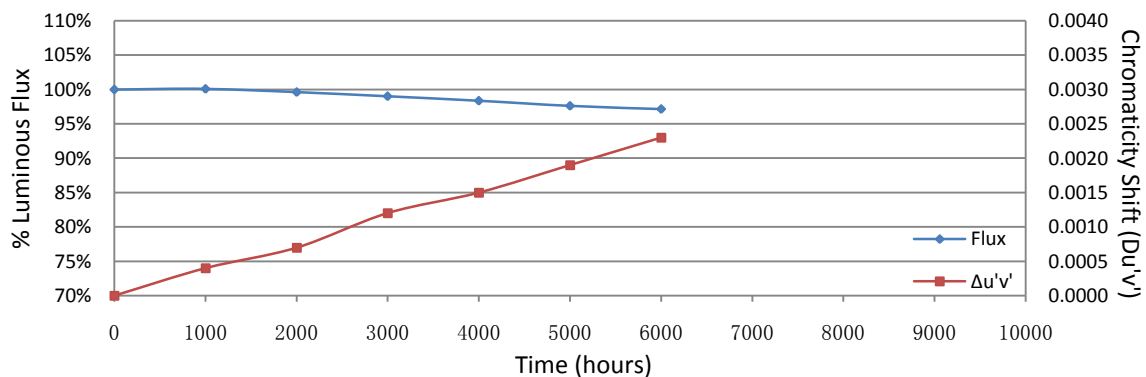

3.3 Data Set 2, 85°C, 100mA (Lumen Maintenance)


No.	V _F (V)	Φ(lm)	Lumen Maintenance (%)					
	0hr(Initial)		1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
26	9.418	108.6	100.18	99.72	98.80	98.07	96.96	96.87
27	9.224	110.5	99.55	98.91	98.28	97.56	96.47	96.11
28	9.386	109.8	99.73	99.09	98.18	97.18	96.36	96.17
29	9.248	111.4	100.09	99.64	98.74	98.29	97.31	97.22
30	9.238	110.4	100.00	99.46	98.46	97.46	96.74	96.47
31	9.231	111.1	100.09	99.82	98.83	98.29	97.39	96.94
32	9.234	110.1	100.09	99.64	98.73	97.91	96.73	96.64
33	9.434	107.6	99.81	99.26	98.33	97.30	97.21	96.84
34	9.062	112.6	99.82	99.47	98.49	97.96	96.27	96.00
35	9.422	108.7	100.18	99.63	98.99	97.98	97.06	96.87
36	9.167	111.3	99.64	99.37	98.65	97.75	96.95	96.77
37	9.256	109.8	99.91	99.27	98.54	97.81	96.72	96.45
38	9.403	109.2	99.82	99.45	98.99	98.17	97.99	97.71
39	9.192	110.9	100.09	99.64	98.83	97.93	96.93	96.57
40	9.149	111.8	100.18	99.55	98.75	98.12	97.14	96.96
41	9.242	109.1	100.09	99.63	98.81	97.89	96.88	96.61
42	9.414	107.8	100.37	99.81	99.07	98.05	97.12	96.85
43	9.258	108.1	100.28	99.81	98.98	98.61	98.33	98.06
44	9.251	109.9	100.09	99.55	99.00	98.09	97.09	96.63
45	9.325	107.8	100.00	99.63	99.07	97.96	97.40	97.22
46	9.237	109.9	100.27	99.82	99.00	98.18	97.00	96.91
47	9.142	109.9	100.09	99.45	98.64	98.00	96.27	95.81
48	9.411	107.8	100.19	99.72	98.98	97.96	96.94	96.75
49	9.117	111.5	99.91	99.46	98.74	98.12	97.22	97.13
50	9.422	108.0	100.28	99.72	98.98	98.43	97.22	97.13
Ave.	9.275	109.7	100.03	99.54	98.75	97.96	97.03	96.79
Med.	9.248	109.9	100.09	99.63	98.80	97.98	97.00	96.84
st dev	0.1104	1.4405	0.2101	0.2301	0.2557	0.3271	0.4715	0.4956
Min.	9.062	107.6	99.55	98.91	98.18	97.18	96.27	95.81
Max.	9.434	112.6	100.37	99.82	99.07	98.61	98.33	98.06

TM-21 Projection:

Test Duration: 6000 hours
Failures Observed: 0
 α : 7.122E-06
 β : 1.008
Calculated L₇₀: 51,000hours
Reported L₇₀: >36,000hours

3.4 Data Set 2, 85°C, 100mA (Chromaticity Shift)

No.	u'	v'	CCT(K)	Chromaticity Shift ($\Delta u'v'$)					
	0hr(Initial)			1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
26	0.2347	0.5168	3472	0.0005	0.0008	0.0012	0.0017	0.0018	0.0023
27	0.2356	0.5146	3468	0.0004	0.0011	0.0019	0.0022	0.0026	0.0032
28	0.2368	0.5186	3390	0.0004	0.0004	0.0011	0.0014	0.0019	0.0024
29	0.2356	0.5185	3426	0.0003	0.0005	0.0010	0.0015	0.0018	0.0021
30	0.2365	0.5158	3426	0.0002	0.0005	0.0011	0.0013	0.0020	0.0023
31	0.2363	0.5181	3409	0.0004	0.0006	0.0011	0.0014	0.0018	0.0021
32	0.2350	0.5137	3495	0.0004	0.0008	0.0014	0.0018	0.0024	0.0027
33	0.2369	0.5151	3423	0.0003	0.0004	0.0010	0.0014	0.0019	0.0022
34	0.2364	0.5159	3429	0.0002	0.0004	0.0009	0.0012	0.0017	0.0021
35	0.2366	0.5172	3411	0.0004	0.0005	0.0009	0.0011	0.0018	0.0021
36	0.2358	0.5159	3449	0.0006	0.0008	0.0011	0.0016	0.0019	0.0022
37	0.2362	0.5168	3425	0.0006	0.0009	0.0011	0.0014	0.0021	0.0023
38	0.2364	0.5173	3414	0.0005	0.0008	0.0012	0.0015	0.0019	0.0021
39	0.2353	0.5140	3483	0.0005	0.0009	0.0013	0.0017	0.0021	0.0022
40	0.2361	0.5166	3430	0.0005	0.0007	0.0011	0.0014	0.0017	0.0018
41	0.2354	0.5147	3472	0.0007	0.0011	0.0014	0.0017	0.0023	0.0023
42	0.2357	0.5150	3460	0.0006	0.0010	0.0014	0.0017	0.0022	0.0023
43	0.2373	0.5144	3418	0.0004	0.0009	0.0013	0.0018	0.0021	0.0025
44	0.2365	0.5146	3440	0.0004	0.0009	0.0014	0.0017	0.0025	0.0030
45	0.2365	0.5155	3432	0.0007	0.0014	0.0020	0.0025	0.0037	0.0035
46	0.2362	0.5151	3444	0.0004	0.0009	0.0014	0.0018	0.0024	0.0018
47	0.2359	0.5137	3468	0.0005	0.0009	0.0014	0.0017	0.0040	0.0047
48	0.2365	0.5171	3414	0.0004	0.0009	0.0014	0.0018	0.0019	0.0019
49	0.2348	0.5161	3475	0.0007	0.0012	0.0015	0.0019	0.0016	0.0013
50	0.2366	0.5156	3427	0.0005	0.0008	0.0011	0.0015	0.0014	0.0012
Ave.	0.2361	0.5159	3440	0.0005	0.0008	0.0013	0.0016	0.0021	0.0023
Med.	0.2362	0.5158	3430	0.0004	0.0008	0.0012	0.0017	0.0019	0.0022
st dev	0.0007	0.0014	27.1646	0.0001	0.0002	0.0003	0.0003	0.0006	0.0007
Min.	0.2347	0.5137	3390	0.0002	0.0004	0.0009	0.0011	0.0014	0.0012
Max.	0.2373	0.5186	3495	0.0007	0.0014	0.0020	0.0025	0.0040	0.0047

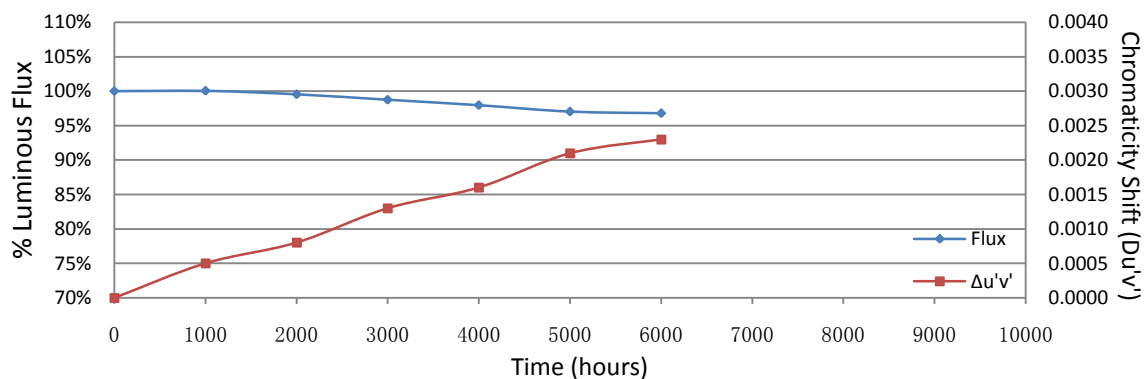

3.5 Data Set 3, 105°C, 100mA (Lumen Maintenance)


No.	V _F (V)	Φ(lm)	Lumen Maintenance (%)					
	0hr(Initial)		1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
51	9.436	107.7	99.81	99.26	98.33	97.31	96.29	95.54
52	9.031	110.6	100.45	100.00	99.01	98.19	96.84	95.84
53	9.254	109.1	100.18	99.63	98.44	97.62	95.78	94.87
54	9.178	110.0	100.27	99.73	98.64	97.45	96.09	95.73
55	9.167	110.1	100.27	99.55	98.55	97.55	96.91	96.00
56	9.093	111.6	100.09	99.55	98.03	97.31	96.06	95.61
57	9.132	110.3	99.82	99.18	98.01	97.28	95.83	94.92
58	9.369	107.8	100.00	99.54	98.52	97.12	97.03	96.57
59	8.994	110.1	100.09	99.36	98.46	97.55	97.00	96.64
60	9.227	110.5	99.91	99.46	98.37	97.38	96.29	95.29
61	9.253	109.4	100.18	99.63	98.63	97.71	96.62	95.80
62	9.306	107.3	100.09	99.44	98.70	97.30	96.92	96.55
63	9.155	111.2	99.91	99.46	98.56	97.84	97.39	96.58
64	9.411	107.4	99.91	99.63	98.60	97.67	95.90	94.97
65	9.314	108.1	99.81	99.07	98.06	97.04	96.58	96.30
66	9.371	106.9	100.09	99.53	98.60	97.66	96.07	95.42
67	9.363	108.4	99.82	99.35	98.34	97.05	95.94	95.39
68	9.217	109.8	99.91	99.45	98.54	97.54	95.90	95.54
69	9.180	109.3	100.18	99.45	98.44	97.26	96.52	96.16
70	9.030	111.7	99.91	99.28	98.21	97.40	96.51	95.97
71	9.398	107.8	100.09	99.54	98.70	97.96	96.47	95.64
72	9.250	108.8	100.09	99.36	98.44	97.52	96.32	95.31
73	9.234	110.6	100.27	99.64	98.64	97.65	95.84	95.48
74	9.598	109.6	100.18	99.45	98.27	97.45	96.81	96.44
75	9.190	109.6	100.18	99.54	98.72	97.81	97.35	96.81
Ave.	9.246	109.3	100.06	99.48	98.47	97.50	96.45	95.81
Med.	9.234	109.6	100.09	99.46	98.52	97.52	96.47	95.73
st dev	0.1420	1.3784	0.1739	0.1867	0.2357	0.2780	0.4861	0.5694
Min.	8.994	106.9	99.81	99.07	98.01	97.04	95.78	94.87
Max.	9.598	111.7	100.45	100.00	99.01	98.19	97.39	96.81

TM-21 Projection:

Test Duration: 6000 hours
Failures Observed: 0
 α : 9.135E-06
 β : 1.011
Calculated L₇₀: 40,000hours
Reported L₇₀: >36,000hours


3.6 Data Set 3, 105°C, 100mA (Chromaticity Shift)

No.	u'	v'	CCT(K)	Chromaticity Shift ($\Delta u'v'$)					
	0hr(Initial)			1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
51	0.2360	0.5154	3446	0.0004	0.0008	0.0012	0.0017	0.0021	0.0023
52	0.2368	0.5134	3444	0.0004	0.0008	0.0012	0.0018	0.0021	0.0022
53	0.2364	0.5163	3425	0.0004	0.0009	0.0017	0.0021	0.0032	0.0037
54	0.2372	0.5166	3398	0.0006	0.0008	0.0012	0.0016	0.0019	0.0021
55	0.2363	0.5157	3435	0.0006	0.0010	0.0015	0.0019	0.0036	0.0042
56	0.2369	0.5165	3410	0.0006	0.0011	0.0017	0.0021	0.0030	0.0035
57	0.2362	0.5154	3442	0.0006	0.0013	0.0020	0.0024	0.0026	0.0028
58	0.2341	0.5153	3505	0.0006	0.0009	0.0013	0.0017	0.0017	0.0020
59	0.2374	0.5151	3408	0.0006	0.0009	0.0014	0.0018	0.0018	0.0020
60	0.2360	0.5144	3457	0.0006	0.0008	0.0013	0.0018	0.0020	0.0024
61	0.2377	0.5134	3417	0.0006	0.0008	0.0013	0.0016	0.0018	0.0022
62	0.2363	0.5145	3446	0.0005	0.0008	0.0013	0.0018	0.0018	0.0020
63	0.2344	0.5143	3509	0.0006	0.0010	0.0016	0.0021	0.0029	0.0038
64	0.2367	0.5163	3417	0.0005	0.0007	0.0013	0.0016	0.0032	0.0045
65	0.2367	0.5168	3412	0.0007	0.0011	0.0016	0.0021	0.0026	0.0031
66	0.2364	0.5147	3441	0.0005	0.0007	0.0012	0.0015	0.0019	0.0013
67	0.2357	0.5161	3449	0.0004	0.0004	0.0006	0.0011	0.0012	0.0012
68	0.2367	0.5156	3424	0.0006	0.0011	0.0012	0.0016	0.0017	0.0015
69	0.2362	0.5177	3417	0.0005	0.0013	0.0013	0.0017	0.0019	0.0018
70	0.2368	0.5160	3418	0.0006	0.0013	0.0019	0.0024	0.0034	0.0042
71	0.2365	0.5181	3405	0.0005	0.0012	0.0016	0.0021	0.0022	0.0022
72	0.2365	0.5169	3417	0.0005	0.0012	0.0019	0.0023	0.0036	0.0046
73	0.2364	0.5161	3429	0.0004	0.0010	0.0015	0.0019	0.0035	0.0041
74	0.2356	0.5151	3462	0.0006	0.0013	0.0021	0.0025	0.0034	0.0036
75	0.2353	0.5152	3471	0.0006	0.0012	0.0015	0.0019	0.0024	0.0015
Ave.	0.2363	0.5156	3436	0.0005	0.0010	0.0015	0.0019	0.0025	0.0027
Med.	0.2364	0.5156	3429	0.0006	0.0010	0.0014	0.0018	0.0022	0.0023
st dev	0.0008	0.0012	28.4673	0.0001	0.0002	0.0003	0.0003	0.0007	0.0011
Min.	0.2341	0.5134	3398	0.0004	0.0004	0.0006	0.0011	0.0012	0.0012
Max.	0.2377	0.5181	3509	0.0007	0.0013	0.0021	0.0025	0.0036	0.0046

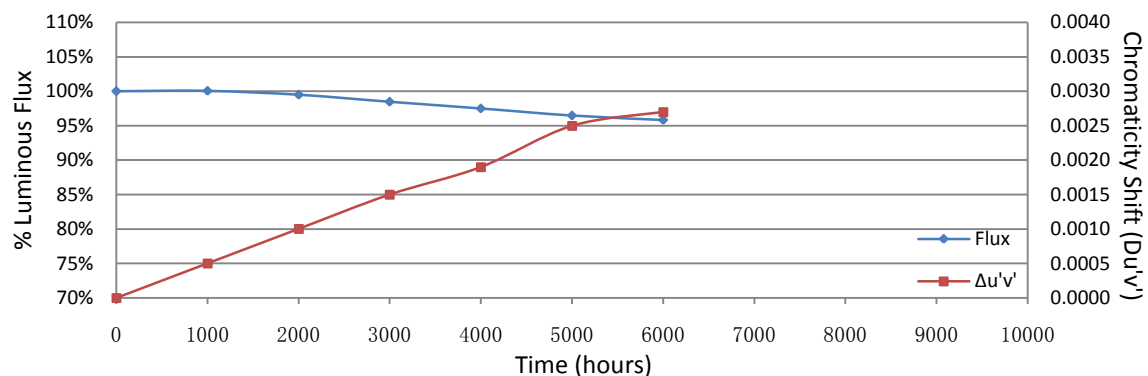


Attachment A – EUT PHOTO

A.1 Mechanical Dimensions (Ta = 25°C)

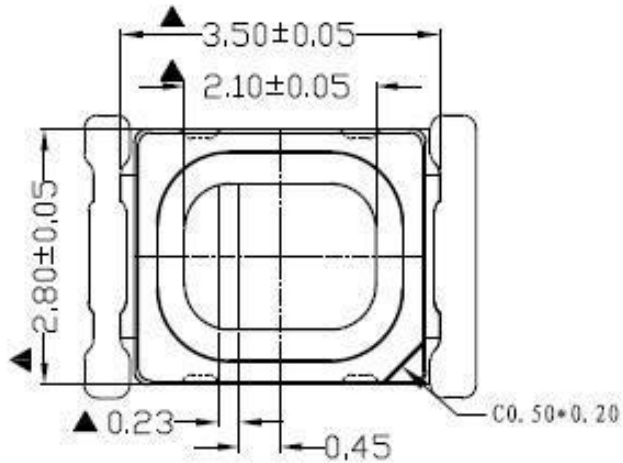

All dimensions are in millimeter

A.2 EUT Photo

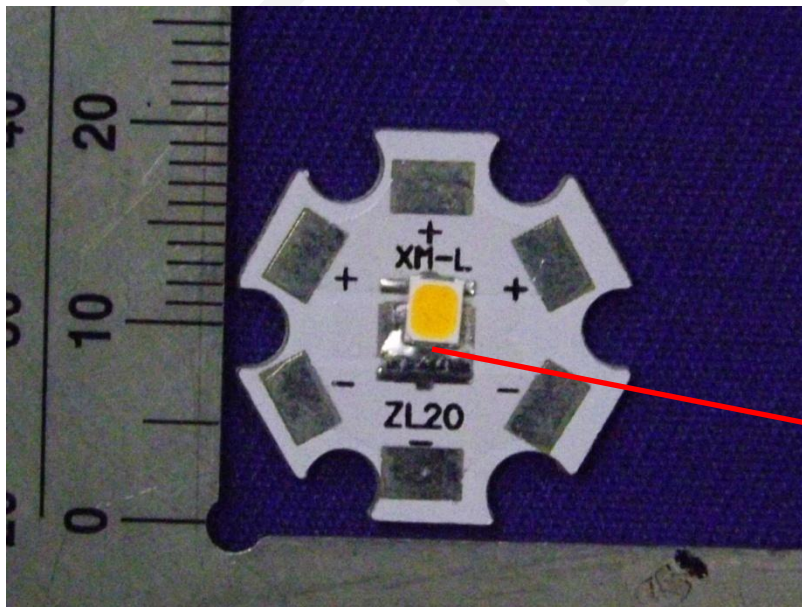

*****END OF REPORT*****